

DETERMINATION OF PHASE TRANSITIONS IN Y-SHAPED, BRANCHED ALKANE, C₁₂₀H₂₄₁CH(C₁₉₅H₃₉₁)C₁₁₉H₂₃ USING RAMAN SPECTROSCOPY

P. A. SURANGA R. WICKRAMARACHCHI¹ & STEPHEN J. SPELLS²

¹**Department of Chemistry, University of Kelaniya, Kelaniya, Sri Lanka**

²**Materials and Engineering Research Institute, City Campus, Sheffield Hallam University, Sheffield S1 1WB, U.K.**

E-mail : suranga@kln.ac.lk

ABSTRACT

Raman spectroscopy has been used to identify solid – solid phase transitions in the symmetrically branched alkane, C₁₂₀H₂₄₁CH(C₁₉₅H₃₉₁)C₁₁₉H₂₃ during real-time heating. The vibrational modes in the region from 1700 to 200 cm⁻¹ were studied. A single phase transition was identified at 87°C ± 5°C in this alkane based on the changes in the band intensities. It was revealed that the crystalline bands show subtle changes whereas the disorder bands show the most significant changes at this transition.


Key words: Monodisperse alkanes, vibrational spectroscopy, crystal structures

INTRODUCTION

Monodisperse linear long chain alkanes (partially deuterated and undeuterated) and their binary mixtures have been successfully studied during the past two decades with a view to relate their crystallisation processes and crystal morphologies to those of linear polyethylene. For an extensive review on the past work on long chain alkanes see Ungar & Zeng (2001). Similarly, monodisperse branched alkanes are becoming popular as model compounds for branched polyethylene. With this aim several single-branched alkanes having short (C₁ and C₄) (Brooke *et al.*, 1996) and long (C₆₁ and C₁₉₅: Y-shaped molecules) (Brooke *et al.*, 2001) branches have been chemically synthesised.

Determination of phase transitions

The crystalline structures of short-branched alkanes and the Y-shaped alkane with a C₆₁ branch have been studied and well established (Ungar & Zeng, 2001). Short branched, symmetrical C₉₆H₁₉₃CH(CH₃)C₉₄H₁₈₉ and C₉₆H₁₉₃CH(C₄H₉)C₉₄H₁₈₉ always produced the once-folded (F2) conformation. This is formed via a short-lived 'NIF' stage. However, short branched, asymmetrical C₁₉₁H₃₈₃CH(CH₃)C₉₉H₁₉₉ shows two semicrystalline forms depending on the crystallisation temperature, *T_c*. Electron density reconstruction has shown that each structure contains alternating amorphous and crystalline layers. They are similar to the 'NIF' structure in linear and symmetrically branched alkanes. Upon cooling these semicrystalline forms transform into a double and triple layer superlattice structures in each case. Y-shaped symmetrical alkane with a long branch, C₁₂₀H₂₄₁CH(C₆₁H₁₂₃)C₁₁₉H₂₃₉, also shows a semicrystalline form at higher temperature (Ungar & Zeng, 2001). A double layer superlattice form has been achieved for the low temperature form. In this superlattice, one layer consists only of the long arm of the molecule while the other layer consists of both the extended short arm and folded long arms. At present, two C₁₉₅-branched symmetrical alkanes are available, one being the deuterated analogue of the other. They are;

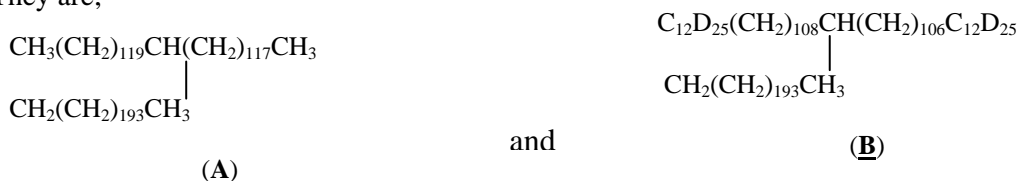

Different crystal structures of C195 – Y shaped alkanes are still being investigated by vibration spectroscopy, small angle X-ray scattering (SAXS) and small angle neutron scattering (SANS). We suspect **A** and **B** also show a high temperature semicrystalline form and a low temperature superlattice structure as in C₆₁- Y shaped branched alkane. The aim of this work is to identify this semicrystalline to superlattice transition in **A** during real-time heating, using Raman spectroscopy. Parallel SAXS work is also being carried out in this regard (Ungar *et al.*, unpublished data). Prior to this analysis, short chain alkane, C₃₄H₇₀ which shows a well established monoclinic to rotator transition, was investigated by Raman spectroscopy in order to establish a suitable methodology for this work (Wickramarachchi & Spells, 2007).

The above transitions are associated with increased conformational disorder in the crystal structure. Raman spectrum is sensitive to these conformational changes. A detailed description of the vibrational modes which are sensitive to conformational

changes in the region of 1700 – 200 cm^{-1} of the Raman spectrum is given in elsewhere (Wickramaarachchi *et al.*, 2007). Only a brief account of these modes is given here. CH_3 rocking region from 900 – 830 cm^{-1} shows various conformational bands. Separate Raman bands have been observed for *tt*-, *gt*-, *gg*- and *tg*- chain ends of an otherwise all-*trans* chain in this region (Kim *et al.*, 1989). The CH_2 twisting band is a combination of two vibrational modes: 1295 cm^{-1} crystalline and 1305 cm^{-1} gauche counterpart (Naylor *et al.*, 1995). The C-C stretching region from 1000 to 1200 cm^{-1} comprises of two strong bands at 1060 and 1130 cm^{-1} arising from *trans* C-C bonds and a broad band centred around 1080 cm^{-1} due to gauche conformers (Naylor *et al.*, 1995; Tarazona *et al.*, 1997). This study intends to determine the semicrystalline to superlattice transition in **A** using the above mentioned conformational bands.

EXPERIMENTAL

A sample (about 3 mg) of **A** was placed on the lid of a DSC pan (Mettler design). This formed the sample holder which was used here. Sample **A** was melt crystallised (0.2 $^{\circ}$ C min^{-1}) in the sample holder to obtain a thin film. Then the sample holder with the sample was covered by a circular aluminium foil to obtain a better temperature control. The diameters of the sample holder and the aluminium foil were roughly equal. A small hole with a 2 mm diameter was made on the aluminium foil to allow the light to pass through. The spectra were collected as a function of temperature between 60 $^{\circ}$ and 130 $^{\circ}$ C using a Renishaw Raman Spectrometer. A Linkam hot stage was used for these heating runs. The hot stage was fixed on to an Olympus microscope stage. A diode laser at 785 nm was used as the excitation source. Laser light was focussed on the sample using a 20 \times microscope objective. The spectra were measured between 1700 and 150 cm^{-1} with a resolution of 2 cm^{-1} .

The analysis of the Raman spectra involved the baseline correction and curve fitting procedures. The curve fitting was performed using GRAMS 32 software.

RESULTS AND DISCUSSION

The Raman spectrum of $\text{C}_{34}\text{H}_{70}$ (Wickramaarachchi & Spells, 2007) demonstrated very clear changes in crystalline and amorphous bands in region 1: CH_2 bending (1600 – 1400 cm^{-1}), region 2: CH_2 twisting (\sim 1300 cm^{-1}), region 3: C-C stretching (1200 – 1000 cm^{-1}) and region 4: CH_3 rocking conformations (\sim 900 cm^{-1}) at the phase transitions of $\text{C}_{34}\text{H}_{70}$ (Wickramaarachchi & Spells, 2007). These regions are illustrated in figures 1 and 2.

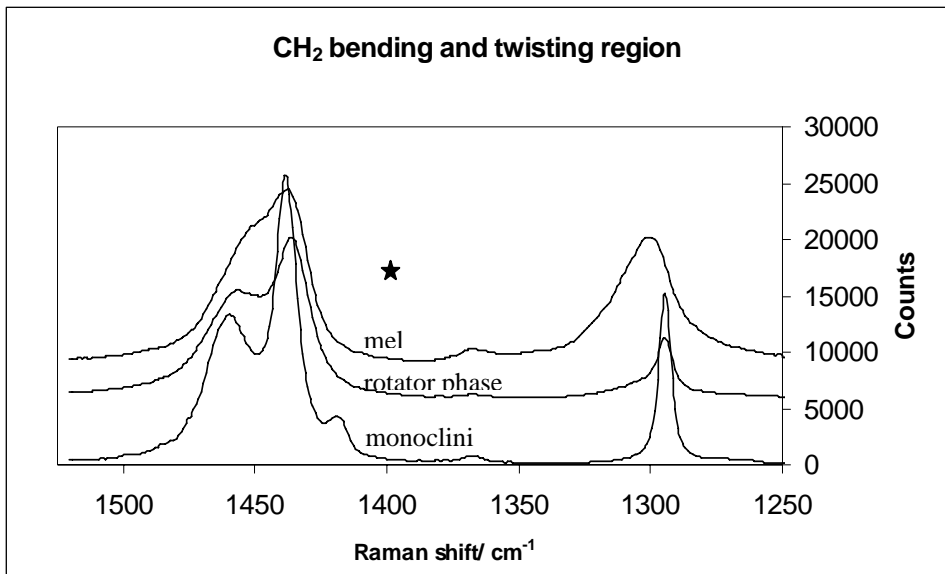


Figure 1 : CH₂ bending (region 1) and twisting (region 2) modes of the Raman spectrum of C₃₄H₇₀ in monoclinic, rotator, and melt phases at 62, 71, and 76 °C respectively.

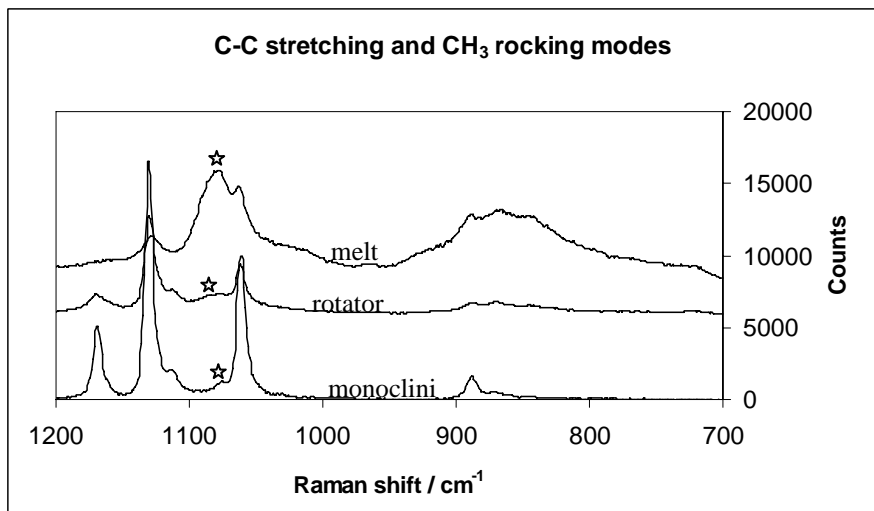


Figure 2 : C-C stretching (region 3) and CH₃ rocking (region 4) modes of C₃₄H₇₀ for different phases at 62, 71, and 76 °C respectively.

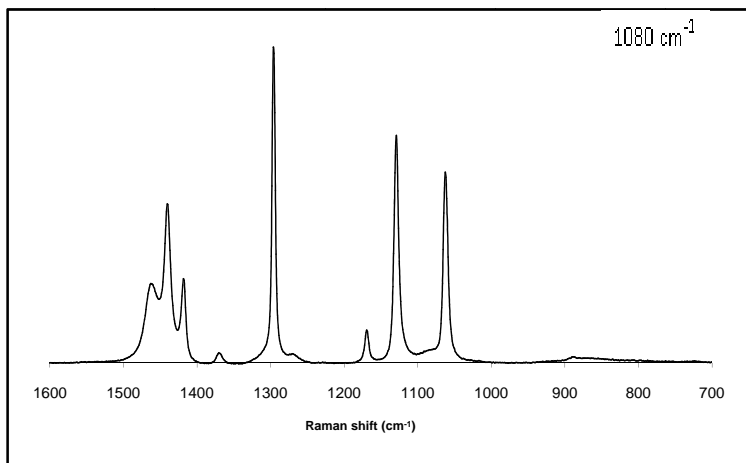


Figure 3 : Raman spectrum of A at 70° C in the region from 1600 to 700 cm⁻¹.

Figure 3 shows the Raman spectrum of A at 70° C. We can identify a gauche band at 1080 cm⁻¹ (*) and CH₃ rocking conformational bands around 900 cm⁻¹ in the spectrum of A even at this relatively low temperature. Although the 1305 cm⁻¹ twisting mode due to gauche conformers is hardly visible in this spectrum, it is identifiable by curve fitting. These observations suggest that branching incorporates some disorder to the crystal lattice. CH₂ bending mode which is sensitive to the lattice geometry was unaffected until melting of the sample. The 1418 cm⁻¹ band which indicates an orthorhombic lattice (Boerio *et al.*, 1970) was observable until melting. This suggests that they keep the original geometry even at higher temperature phase.

The CH₂ twisting and the C-C stretching regions of the Raman spectra collected from 60° C up to melting, during a stepwise, real-time heating run of sample A are shown in figures 4 and 5 respectively. Figure 6 shows an expanded view of the 1080 cm⁻¹ band. This band was somewhat noisy so the spectra have been smoothed by 30% using the GRAMS 32AI Fourier smoothing function. From 60° to 82° C we can observe a gradual increase of the intensity of 1080 cm⁻¹ gauche band with increasing temperature. Then from 82° C to 96° C this increase become very rapid and slows down again from 96° C and above until just below melting (118° C) of the sample. When the sample starts melting it increases very rapidly and in the melt spectrum both 1060 and 1130 cm⁻¹ bands disappear and the 1080 cm⁻¹ band dominates (Figure 5). In figure 6 only a part of the melt spectrum is shown. The rapid increase of the 1080 cm⁻¹ band from 82° C to 96° C could be due to the phase transition occurring in this

Determination of phase transitions

temperature range. The NIF state is more disordered and therefore the gauche content of chains would be expected to be large.

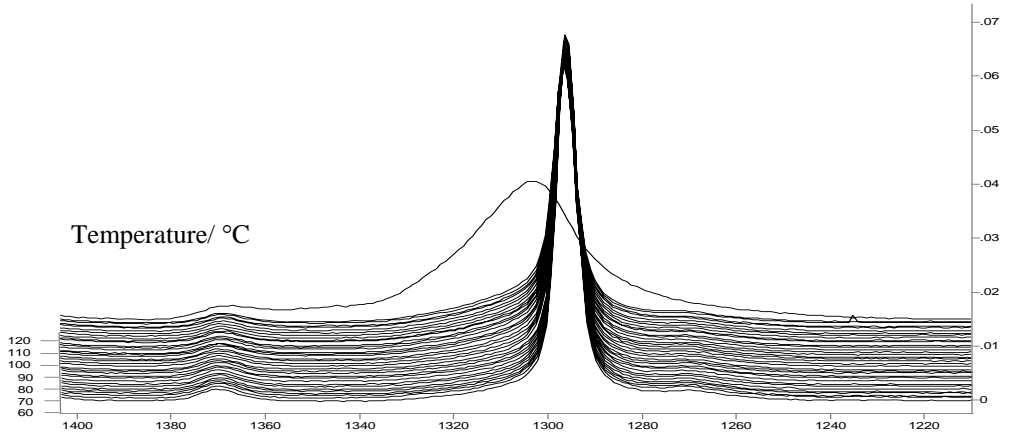


Figure 4: The waterfall arrangement of the CH₂ twisting mode of the Raman spectra of A during stepwise heating. The spectra are arranged from 60° to 128° C at 2° intervals in an upward direction.

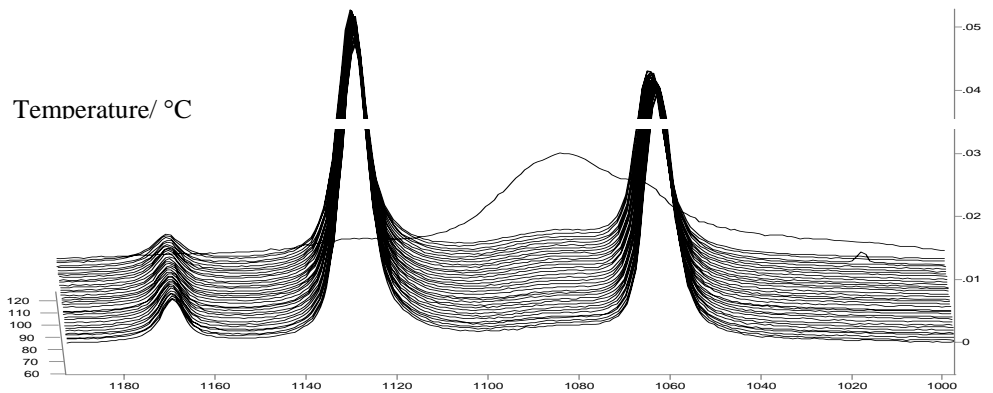


Figure 5: The waterfall arrangement of C-C stretching mode in the Raman spectra of A during stepwise heating. The spectra are arranged from 60° to 128° C at 2° intervals in an upward direction.

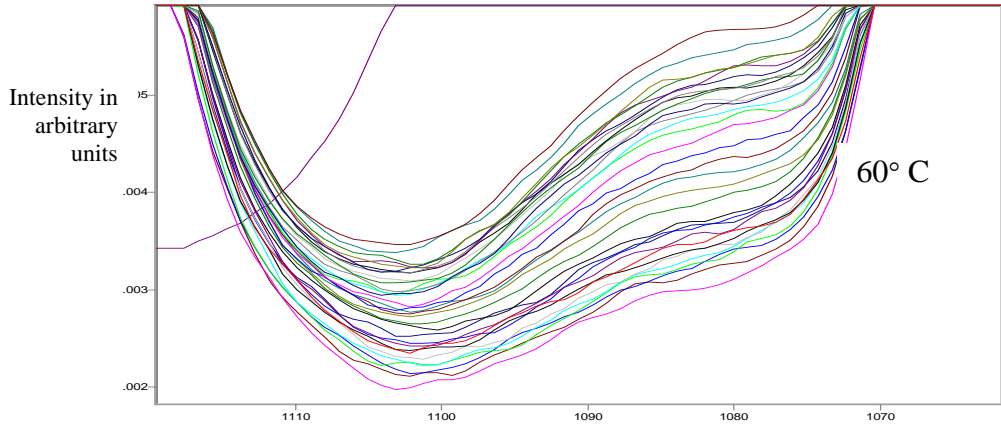


Figure 6 : An expanded, overlaid view of the 1080 cm^{-1} band from 60° C to melting at 2° interval during a stepwise heating run of sample A.

The areas of crystalline and disorder bands in regions 2, 3 and 4 were determined by curve fitting. The changes of each of the bands in regions 2, 3 and 4 in some runs of sample **A** are illustrated in figures 7 and 8. The most significant changes could be observed only in the disorder bands. No significant changes at the phase transition were observed in the strong crystalline bands (1295 , 1130 and 1060 cm^{-1}). The time associated with the chart title is the total scan time of each spectrum. The grating of the Raman spectrometer slipped sometimes while the experiments were in progress. This caused significant intensity differences between spectra as well as frequency. The frequency shift was corrected by calibrating the spectrometer against a silicon band at 520 cm^{-1} . In order to correct the intensity difference the spectra were normalised to the integrated area of the C-C stretching region. Raw data are represented for runs where the grating slippage did not occur. The figures at melting are omitted to expand the scale.

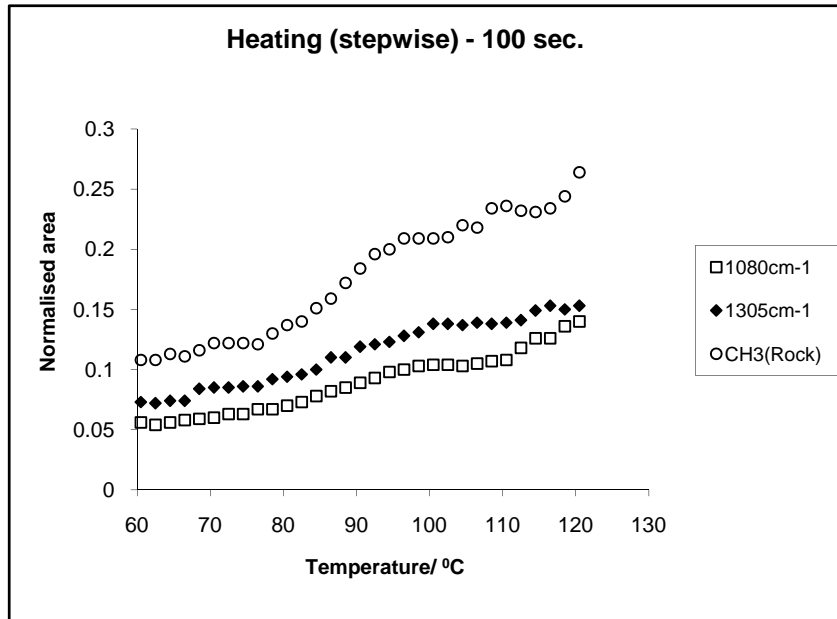


Figure 7 : The variation of area of the disorder bands in regions 2, 3 and 4 with temperature during a stepwise heating run at $1^{\circ}\text{C min}^{-1}$.

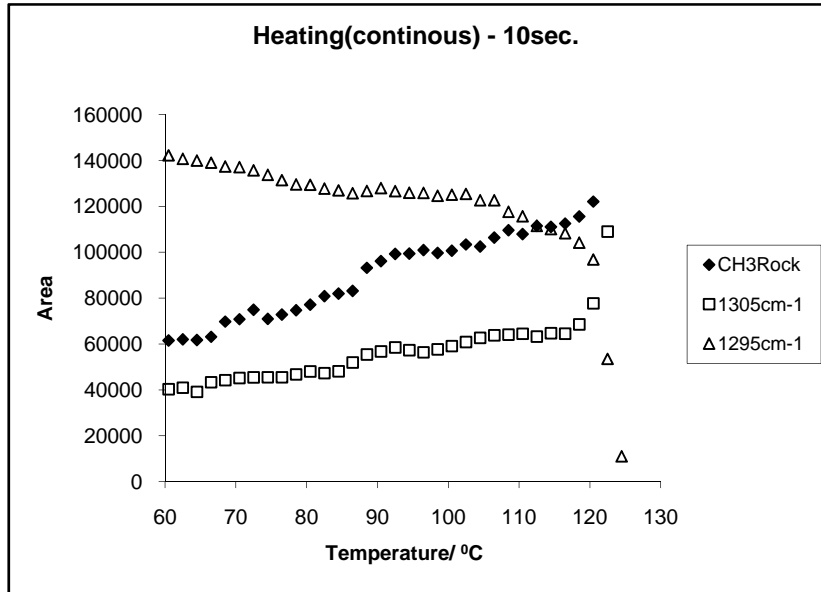


Figure 8 : The variation of area of the bands in regions 2, 3 and 4 with during a continuous heating run at $1^{\circ}\text{C min}^{-1}$.

In figure 7 we could observe an increase in the relative intensities of the disorder bands between about 82°C and 96°C (also see figure 6) and in figure 8 this was observed from 84° to 94°C. In addition, in figure 8 we could see a change of the gradient of the 1295 cm⁻¹ crystalline band around 84° C. These changes were identified as the superlattice to semicrystalline phase transition as we know that this transition is associated with the disordering of the crystal structure (Ungar & Zeng, 2001). SAXS studies too has shown a similar temperature change for this transition (Ungar & Zeng, unpublished data).

CONCLUSIONS

Vibrational spectroscopy is sensitive to both the crystalline structure as well as to the conformational changes. Here use is made of Raman spectroscopy to identify the superlattice to semicrystalline transition which is associated with an increase in the conformational disorder, in branched chain alkane sample A. Regions 1, 2, 3, and 4 of the Raman spectrum of sample A were monitored. No changes could be observed in region 1 whereas the rest of the regions were found to be sensitive to the transition. We identified a single solid phase transition from Raman data. The changes in the crystalline bands were subtle whereas the disorder bands showed the most significant changes at this transition. Raman results suggest that this phase transition occurs around $\sim 87^\circ \pm 5^\circ$ C during heating. This figure is very close to the figure obtained from SAXS data.

ACKNOWLEDGMENT

We wish to thank Professor Goran Ungar and Dr. Xiang-Bing Zeng (University of Sheffield, UK) for useful discussions. We are also indebted to Dr. Chris Sammon (Sheffield Hallam University, UK) for assisting us with the Raman measurements.

REFERENCES

- Boerio, F.J., & J.L.Koenig. 1970. Raman scattering in crystalline polyethylene. *Journal of Chemical Physics* 52(7): 3425-3431.
- Brooke, G.M., S. Burnett, S. Mohammed, D. Proctor & M.C. Whiting. 1996. A versatile process for the syntheses of very long chain alkanes, functionalised derivatives and some branched chain hydrocarbons. *Journal of the Chemical Society, Perkin Transactions 1*: 1635-1645.
- Brooke, G.M., C. Farren, A. Harden & M.C. Whiting. 2001. Syntheses of very long chain alkanes terminating in polydeuterium-labelled end-groups and some very large single-branched alkanes including Y-shaped structures. *Polymer* 42: 2777-2784.
- Kim, Y., H.L. Strauss & R.G. Snyder. 1989. Conformational disorder in the binary mixture pentacontane/hexatetracontane: a vibrational spectroscopic study. *Journal of Physical Chemistry* 93: 485-490.
- Naylor, C.C., R. Meier, B.J. Kip, P.J. Williams, S.M. Mason, N. Conroy & D.L. Gerrard. 1995. Raman Spectroscopy employed for the determination of the intermediate phase in polyethylene. *Macromolecules* 28: 2969-2978.
- Tarazona, A., E. Koglin, B. Coussens & R.J. Meier. 1997. Conformational dependence of Raman frequencies and intensities in alkanes and polyethylene. *Vibrational Spectroscopy* 14: 159-170.
- Ungar, G. & X.B. Zeng. 2001. Learning polymer crystallization with the aid of linear, branched and cyclic model compounds. *Chemical Reviews* 101: 4157-4188.
- Ungar, G. & X.B. Zeng, University of Sheffield, UK, unpublished data.
- Wickramarachchi, P.A.S.R., S.J. Spells & D.S.M. de Silva. 2007. Study of disorder in different phases of tetratriacontane and a binary alkane mixture, using vibrational spectroscopy. *Journal of Physical Chemistry B* 111: 1604-1609.